


AD-A143 188 PHYSICAL PROPERTIES OF CDTF FILMS GROWN BY HOTWALL AND 1/1
MOLECULAR BEAM TECHNIQUES(U) NORTH CAROLINA STATE UNIV
RALEIGH J F SCHETZINA JUN 84 ARO-17772.11-EL
UNCLASSIFIED DARG29-81-K-0055 F/G 20/2 NL



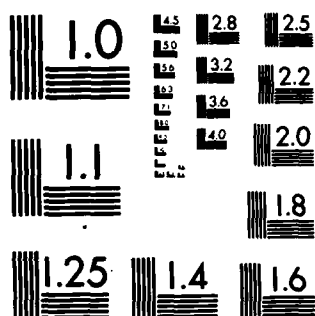

MICROCOPY RESOLUTION TEST CHART
NATIONAL BUREAU OF STANDARDS-1963-A

DD FORM 1 JAN 73

AD-A143 180

(2)

READ INSTRUCTIONS BEFORE COMPLETING FORM	
1. REPORT NUMBER ARO 17772.11-EL	2. GOVT ACCESSION NO. N/A
3. RECIPIENT'S CATALOG NUMBER N/A	
4. TITLE (and Subtitle) Physical Properties of CdTe Films Grown by Hotwall and Molecular Beam Techniques	5. TYPE OF REPORT & PERIOD COVERED Final 1 Mar 81-28 Feb 84
7. AUTHOR(s) J. F. Schetzina	6. PERFORMING ORG. REPORT NUMBER
9. PERFORMING ORGANIZATION NAME AND ADDRESS	8. CONTRACT OR GRANT NUMBER(s) DAAG29-81-K-0055
11. CONTROLLING OFFICE NAME AND ADDRESS U. S. Army Research Office Post Office Box 12211 Research Triangle Park, NC 27709	10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)	12. REPORT DATE June 1984
	13. NUMBER OF PAGES
	15. SECURITY CLASS. (of this report) Unclassified
	15a. DECLASSIFICATION/DOWNGRADING SCHEDULE
16. DISTRIBUTION STATEMENT (of this Report) Approved for public release; distribution unlimited.	
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report) NA	
18. SUPPLEMENTARY NOTES The view, opinions, and/or findings contained in this report are those of the author(s) and should not be construed as an official Department of the Army position, policy, or decision, unless so designated by other documentation.	
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) CdTe, Hg CdTe, molecular beam epitaxy, sapphire, GaAs	
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) Results have shown that MBE and hotwall MBE techniques can be employed to grow high quality epitaxial CdTe films, suitable for use as substrates for Hg CdTe film growth, using alternative substrates. In particular,	

DTIC FILE COPY

DTIC
ELECTE
JUL 19 1984

DD FORM 1 JAN 73 1473

EDITION OF 1 NOV 65 IS OBSOLETE

UNCLASSIFIED

84 07 12 062

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

Unclassified

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

Micrometer

ARO 17772.11-EL

20. ABSTRACT CONTINUED:

CdTe / (0001) sapphire and CdTe / (100) GaAs provide viable alternatives to bulk CdTe for use as substrates in the 2-5 μm and 8-14 μm IR regions, respectively.

The most recent results indicate that layers grown by hotwall MBE are at least comparable to and, perhaps, superior to MBE grown films. This is an important finding because it implies that the CdTe epitaxial film growth process on these alternatives substrates may be "scaled-up" to meet production needs for substrate using batch processing techniques.

Accession For	
NTIS GRA&I	<input checked="" type="checkbox"/>
DTIC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By	
Distribution/	
Availability Codes	
Dist	Avail and/or Special
A-1	



Unclassified

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

SUMMARY OF ACCOMPLISHMENTS AT NCSU UNDER
ARO SUPPORT OF INFRARED MATERIALS RESEARCH AT NCSU

March 1, 1984 - February 29, 1984

Publications and presentations which describe the work completed under
ARO contract DAAG29-81-K-0055 are listed below:

PUBLICATIONS

"Molecular Beam Source for High Vapor Pressure Materials", J. Vac. Sci. Tech.
20, 134 (1982) (T.H. Myers and J.F. Schetzina).

"Properties of CdTe-Te Alloy Films Prepared Using Molecular Beams", J. Appl. Phys.
53, 5697 (1982) (T.H. Myers, A.W. Waltner, and J.F. Schetzina).

"Properties of CdTe/InSb Heterostructures Prepared by Molecular Beam Epitaxy",
J. Appl. Phys. 53, 9232 (1982) (T.H. Myers, Yawcheng Lo, S.R. Jost, and J.F.
Schetzina).

"Growth of CdTe Films on Sapphire by Molecular Beam Epitaxy", Appl. Phys. Lett.
42, 247 (1983) (T.H. Myers, Yawcheng Lo, R.N. Bicknell, and J.F. Schetzina).

"Effects of Surface Preparation on the 77 K Photoluminescence of CdTe", J. Appl.
Phys. 54, 4232 (1983) (T.H. Myers, S.T. Edwards, A.F. Schreiner, and J.F. Schetzina).

"Growth of CdTe Films on Silicon by Molecular Beam Epitaxy", J. Appl. Phys. 54,
4238 (1983) (T.H. Myers, Yawcheng Lo, R.N. Bicknell, H.H. Stadelmaier, and
J.F. Schetzina).

"Growth of Low Dislocation Density CdTe Films on Hydroplaned CdTe Substrates by
Molecular Beam Epitaxy", J. Vac. Sci. Tech. A1, 1598 (1983) (T.H. Myers, T.J.
Magee, R.D. Ormond, and J.F. Schetzina).

"Photoluminescence from CdTe/Sapphire Films Prepared by Molecular Beam Epitaxy",
J. Appl. Phys. 54, 6785 (1983) (S.T. Edwards, A.F. Schreiner, T.H. Myers, and
J.F. Schetzina).

"Growth of (100) CdTe Films of High Structural Perfection on (100) GaAs Substrates by Molecular Beam Epitaxy", Appl. Phys. Lett., February 1 (1984) (with R.N. Bicknell, R.W. Yanka, N.C. Giles, T.J. Magee, C. Leung, H. Kawayoshi, and J.F. Schetzina).

"Growth of CdTe Films on Alternative Substrates by Molecular Beam Epitaxy", J. Vac. Sci. Tech. A 2, 423, (1984) (with R.N. Bicknell, T.H. Myers, and J.F. Schetzina).

PAPERS PRESENTED AT PROFESSIONAL MEETINGS

"Molecular Beam Growth System for High Vapor Pressure Materials", Bull. Am. Phys. Soc. 26, 1198 (1981) (T.H. Myers and J.F. Schetzina).

"Heteroepitaxial growth of CdTe Films by Molecular Beam Epitaxy", Bull. Amer. Phys. Soc. 27, 751 (1982) (Yawcheng Lo, R.N. Bicknell, T.H. Myers, and J.F. Schetzina).

"Homoepitaxial Growth of CdTe Films by Molecular Beam Epitaxy", Bull. Amer. Phys. Soc. 27, 751 (1982) (T.H. Myers, Yawcheng Lo, R.N. Bicknell, and J.F. Schetzina).

"Growth of Low Dislocation Density CdTe Films on Hydroplaned CdTe Substrates by Molecular Beam Epitaxy", 1983 U.S. Workshop on MCT, (Dallas) (T.H. Myers, R. Ormond, T. Magee, and J.F. Schetzina).

"Growth of CdTe Films on Alternative Substrates by Molecular Beam Epitaxy", National Symposium of the American Vacuum Society, (Boston) (1983) (R.N. Bicknell, T.H. Myers, and J.F. Schetzina).

"Properties of CdTe Grown Epitaxially on Sapphire by MBE", Proceedings of IRIS Infrared Detector Conference, (Boulder) (1983) (T.H. Myers, S.R. Jost, H.S. Cole, H.H. Woodbury, and J.F. Schetzina).

"Photoluminescence Studies of Epitaxial CdTe Films", SESAPS Meeting, (Columbia) (1983) (with N.C. Giles, R.N. Bicknell, T.H. Myers, and J.F. Schetzina).

"Photoconductivity Enhancement from Indium Incorporation in CdTe Films Grown on Sapphire by Molecular Beam Epitaxy", (Columbia) (1983) (T.H. Myers, and J.F. Schetzina).

"Properties of CdTe/Sapphire Epilayers Grown by Molecular Beam Epitaxy", Amer. Phys. Soc. March Meeting, (Detroit) (1984) (with R.W. Yanka, N.C. Giles, R.N. Bicknell, T.H. Myers, and J.F. Schetzina).

"Photoluminescence Studies of Epitaxial CdTe Films", Amer. Phys. Soc. March Meeting, (Detroit) (1984) (N.C. Giles, R.N. Bicknell, T.H. Myers, and J.F. Schetzina).

"Reflectance of AlAs-GaAs and InGa-GaAs Superlattices", Amer. Phys. Soc. March Meeting, (Detroit) (1984) (D.K. Blanks, W.D. Laidig, and J.F. Schetzina).

INVITED PAPERS AND COLLOQUIA

"Growth of CdTe on Alternative Substrates by MBE", DARPA IR Focal Plane Contractors Meeting, (Washington) (1982) (J.F. Schetzina).

"MBE Growth and Properties of CdTe on Alternative Substrates", General Electric Electronics Laboratory, Syracuse, NY (1983) (J.F. Schetzina).

"Properties and Applications of CdTe/Sapphire and CdTe/GaAs Thin Films", Physics, Duke University (1983) (J.F. Schetzina).

"Growth and Properties of CdTe Films on Alternative Substrates", General Electric Corporate Research Laboratory, Schenectady, NY (1983) (J.F. Schetzina).

"MBE Growth of CdTe/Sapphire and CdTe/GaAs Films", Ford Aerospace Laboratory, Newport Beach, CA (1983) (J.F. Schetzina).

STUDENTS SUPPORTED AT NCSU UNDER ARO CONTRACT DAAG29-81-K-0055

Yawcheng Lo, MS in Physics, 1982.

T.H. Myers, PhD in Physics, 1983.

R.W. Yanka, MS in Physics expected in June, 1984.

R.N. Bicknell, PhD in Physics expected in June, 1985.

D.H. Hinson, PhD in Physics expected in June, 1985.

N.C. Giles, PhD in Physics expected in June, 1986.

D.K. Blanks, Post-Doctoral Research Associate.

PRINCIPAL RESULTS OF RESEARCH

The interested reader is referred to the above publications for a full description of the results obtained at NCSU under ARO contract DAAG29-81-K-0055. In addition, the principal investigator (J.F. Schetzina) may be reached at (919) 737-2515 if further details of the completed work are desired.

Briefly, at NCSU we have shown that MBE and hotwall MBE techniques can be employed to grow high quality epitaxial CdTe films, suitable for use as substrates for Hg CdTe film growth, using alternative substrates. In particular, CdTe / (0001) sapphire and CdTe / (100) GaAs provide viable alternatives to bulk CdTe for use as substrates in the 2-5 μm and 8-14 μm IR regions, respectively. The above layers, grown at NCSU by MBE and hotwall MBE, show sharp x-ray diffraction patterns, low line dislocation densities (less than or equal to $10^4/\text{cm}^2$ for CdTe/(100) GaAs), large photoconductivity and exhibit a very bright photoluminescence dominated by a narrow (~ 11 meV) near-edge peak of excitonic origin. Many of the CdTe layers on both sapphire and GaAs exhibit edge luminescence at room temperature, which is further evidence of their high quality.

Our most recent results indicate that layers grown by hotwall MBE are at least comparable to and, perhaps, superior to MBE grown films. This is an important finding because it implies that the CdTe epitaxial film growth process on these alternatives substrates may be "scaled-up" to meet production needs for substrate using batch processing techniques.

Work at NCSU dealing with CdTe film growth on sapphire and GaAs along with detailed structural, optical, and electrical characterization studies, is continuing at the present time under ARO contract DAAG29-84-K-0039.

END

FILMED

8